


## 6.5 METER TELESCOPE

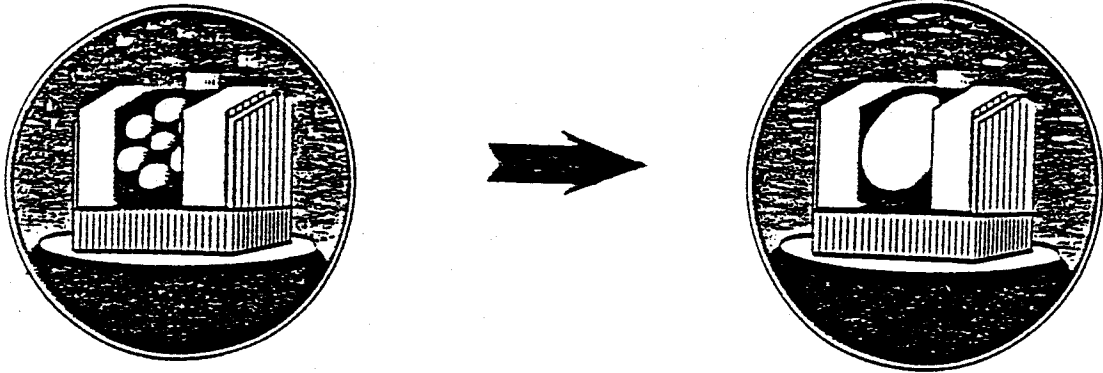

### **MMT Conversion Technical Memorandum #94-3**

Destructive Stress Tests of the 6.5 m Loadspreader Flexures

Shawn Callahan and Marion McEuen

March 1994

# Destructive stress tests of the 6.5m loadspreader flexures.

Shawn Callahan and Marion McEuen  
Multiple Mirror Telescope  
March 10, 1994

## 1.0 Abstract

This report examines two experimental tests of the loadspreader flexures. Both annealed and heat treated flexures were tested with applied shear forces and applied bending moments. This report concludes that heat treated flexures have the best material properties and margin of safety.

## 2.0 Introduction

All of the test flexures were fabricated from annealed 4340 high alloy steel from Jorgensen Steel. Half of the test flexures were then heat treated at the Steward Observatory Mirror lab to an average Rockwell C hardness of 47; the remaining half were tested as originally annealed from the manufacturer. All of the following tests were performed on both the annealed and the heat treated flexures.

## 3.0 Test results

The proportional limit of a material is defined as the point where the stress-strain, force-displacement, or moment-rotation curves begin to deviate from a straight line.

The yield point is usually defined as the point where the permanent strain is 0.002 -0.005. For this report, the yield point was determined using a permanent strain of 0.005.

All calculations of the stress and strain use a minimum cross section of the flexure equal to 6.1 mm.

### 3.1 Shear Test

The first test applied shear force to a flexure while recording the displacement (Figure 1.) The results from this test can be seen in Figure 2. The corresponding shear-strain curves can be seen in Figure 3.

TABLE 1.

Shear Test	Proportional Limit (N)	Yield Point (N)	Proportional Limit (MPa)	Yield Point (MPa)
Annealed	9,700	10,300	320	340
Heat treated	10,500	14,600	360	~500

### 3.2 Moment Test

The second test applied a moment to the shoulder screw and measured rotation of the flexure (Figure 4). The results of the moment versus puck rotation test can be seen in Figure 5. Figure 6 shows the derived normal stress at the minimum cross section of the flexure versus angular rotation.

TABLE 2.

Moment Test	Proportional Limit (N-mm)	Yield Point (N-mm)	Proportional Limit (MPa)	Yield Point (MPa)
Annealed	6,000	12,000	300	580
Heat Treated	14,000	40,000	600	~1800

## 4.0 Conclusions

The test results taken together with the following considerations show that heat treated flexures have acceptable material properties:

1. The nominal maximum *lateral* force applied by the loadspreader to each puck is 833N (reference 1). If the proportional limit is the maximum permissible shear force then the factor of safety is 11.6 for the annealed flexure and 12.6 for the heat treated flexure.
2. Finite Element Models of the 3-puck loadspreader show that the maximum principal stress for 1000 N *axial* loads is 57.3 MPa (reference 2). The nominal maximum axial load applied by the actuators is less than 1500N (reference 1). If the proportional limit is the maximum permissible normal stress then the factor of safety is 3.5 for the annealed flexure and 7.0 for the heat treated flexure.

3. In the unlikely occurrence of a complete failure of a ball decoupler, a 10 mm lateral displacement of the mirror would cause the flexures of the two puck loadspreader to rotate 4.5 degrees. Extrapolating figure 5, the corresponding moments applied to the glass would be 23,000 N-mm for annealed flexures and 120,000 N-mm for heat treated flexure. These moments do not take into account the strain of the glue joint between the puck and the mirror. Glue strain has the effect of decreasing the moment applied to the flexure.

4. The endurance limit of a material is defined as the stress limit where fatigue failure will not occur *no matter how great the number of cycles*. The mean endurance limit is about 0.5 times the yield strength. For the annealed flexure this would correspond to 290 MPa. The published endurance limit for heat treated 4340 steel with a yield strength of 1790 MPa is 668 MPa (reference 4). If the endurance limit is the maximum permissible normal stress then the factor of safety is 3.4 for the annealed flexure and 7.8 for the heat treated flexure.

5. Heat treatment of the flexures relieves machining-induced stress. This has the effect of increasing the reliability and uniformity of the flexures.

## 5.0 List of Figures

Figure 1. Shear test set-up.

Figure 2. Force vs. Displacement (Shear Test).

Figure 3. Shear vs. Strain (Shear Test).

Figure 4. Moment test set-up.

Figure 5. Moment vs. Rotation (Moment Test).

Figure 6. Normal Stress vs. Rotation (Moment Test).

## 6.0 References


1) BCV Report No. 3, MMT "LATERAL SUPPORT SYSTEM - Whiffle Tree Supports at Back Plate- Axial Correction"

2) Callahan, S.P., "Analysis and Design of the Glue Joint, Pucks, and Loadspreader Used in the 6.5m Mirror Support System", *MMT Conversion Technical Memorandum #93-1*, 1993

3) Callahan, S.P., "Two Puck Loadspreader: Stress Due to Ball Decoupler Failure", *MMT Conversion Technical Memorandum #94-3*, 1994

4) Shigley, J.E., "Mechanical Engineering Design"

REVISIONS		
REV	DESCRIPTION	DATE

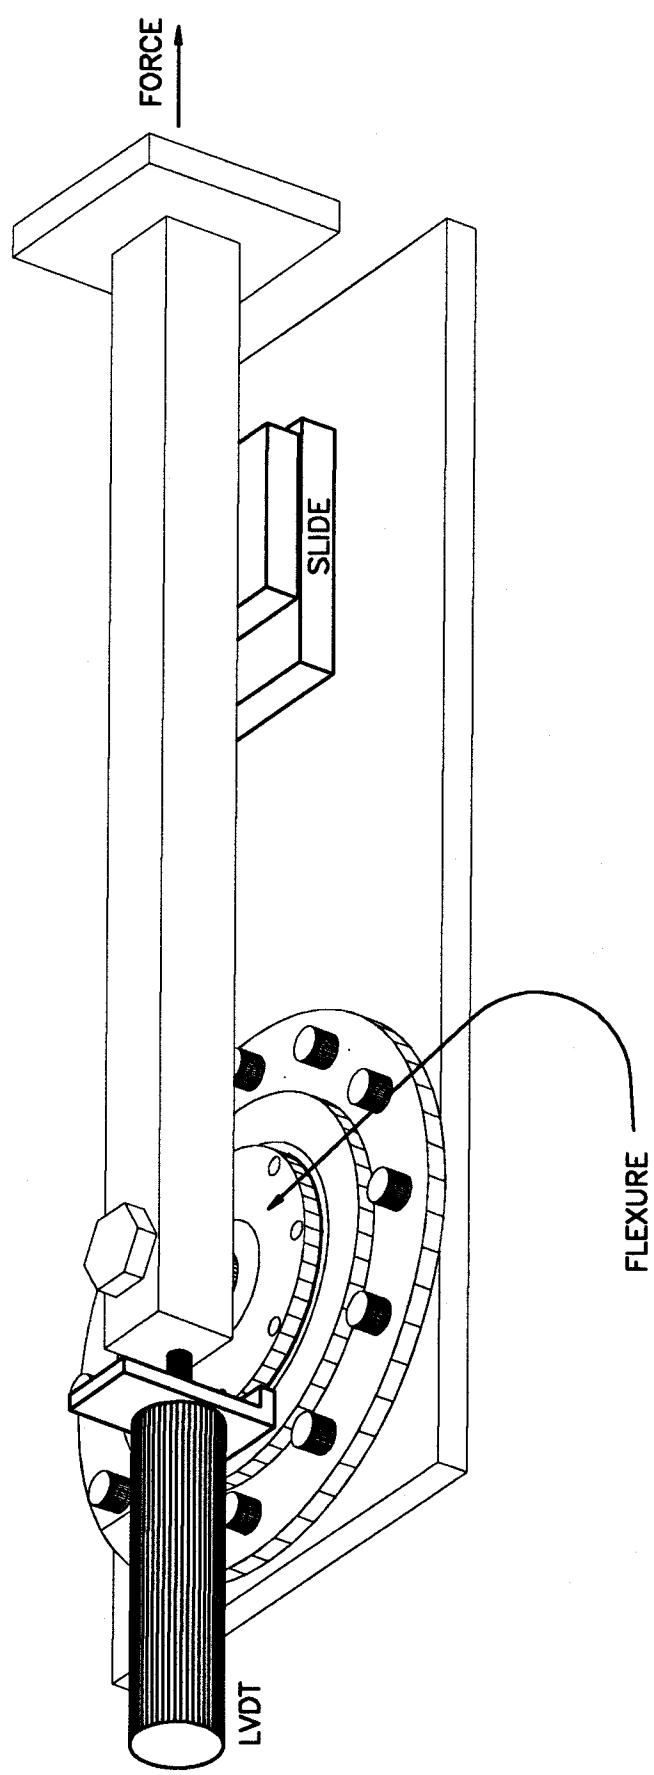

UNLESS OTHERWISE SPEC.	DRAWN BY:	DATE:	UNIVERSITY OF ARIZONA & SMITHSONIAN INSTITUTION MULTIPLE MIRROR TELESCOPE OBSERVATORY TUCSON, ARIZONA 85721
TOLERANCES ON:	M.D. MCGEUN	02/21/94	
DECIMALS	CHECKED BY:		TITLE:
XX ±.010			FLEXURE TEST FIXTURE 1
XX ±.06	SHOP CHECK BY:		SCALE:
FRACTIONS			1" = 2"
ANGLES	APPROVED BY:		REV.
±1/16 ±0°30'			MMT0024
DIMENSIONS ARE IN:	APPROVED BY:		CAD FILE:
ENGLISH & METRIC			MMT0024
MATERIAL			SHEET NO.
1" STEEL ROUND			1
STOCK			
FINISH			

FIGURE 1.

FORCE vs. DISPLACEMENT

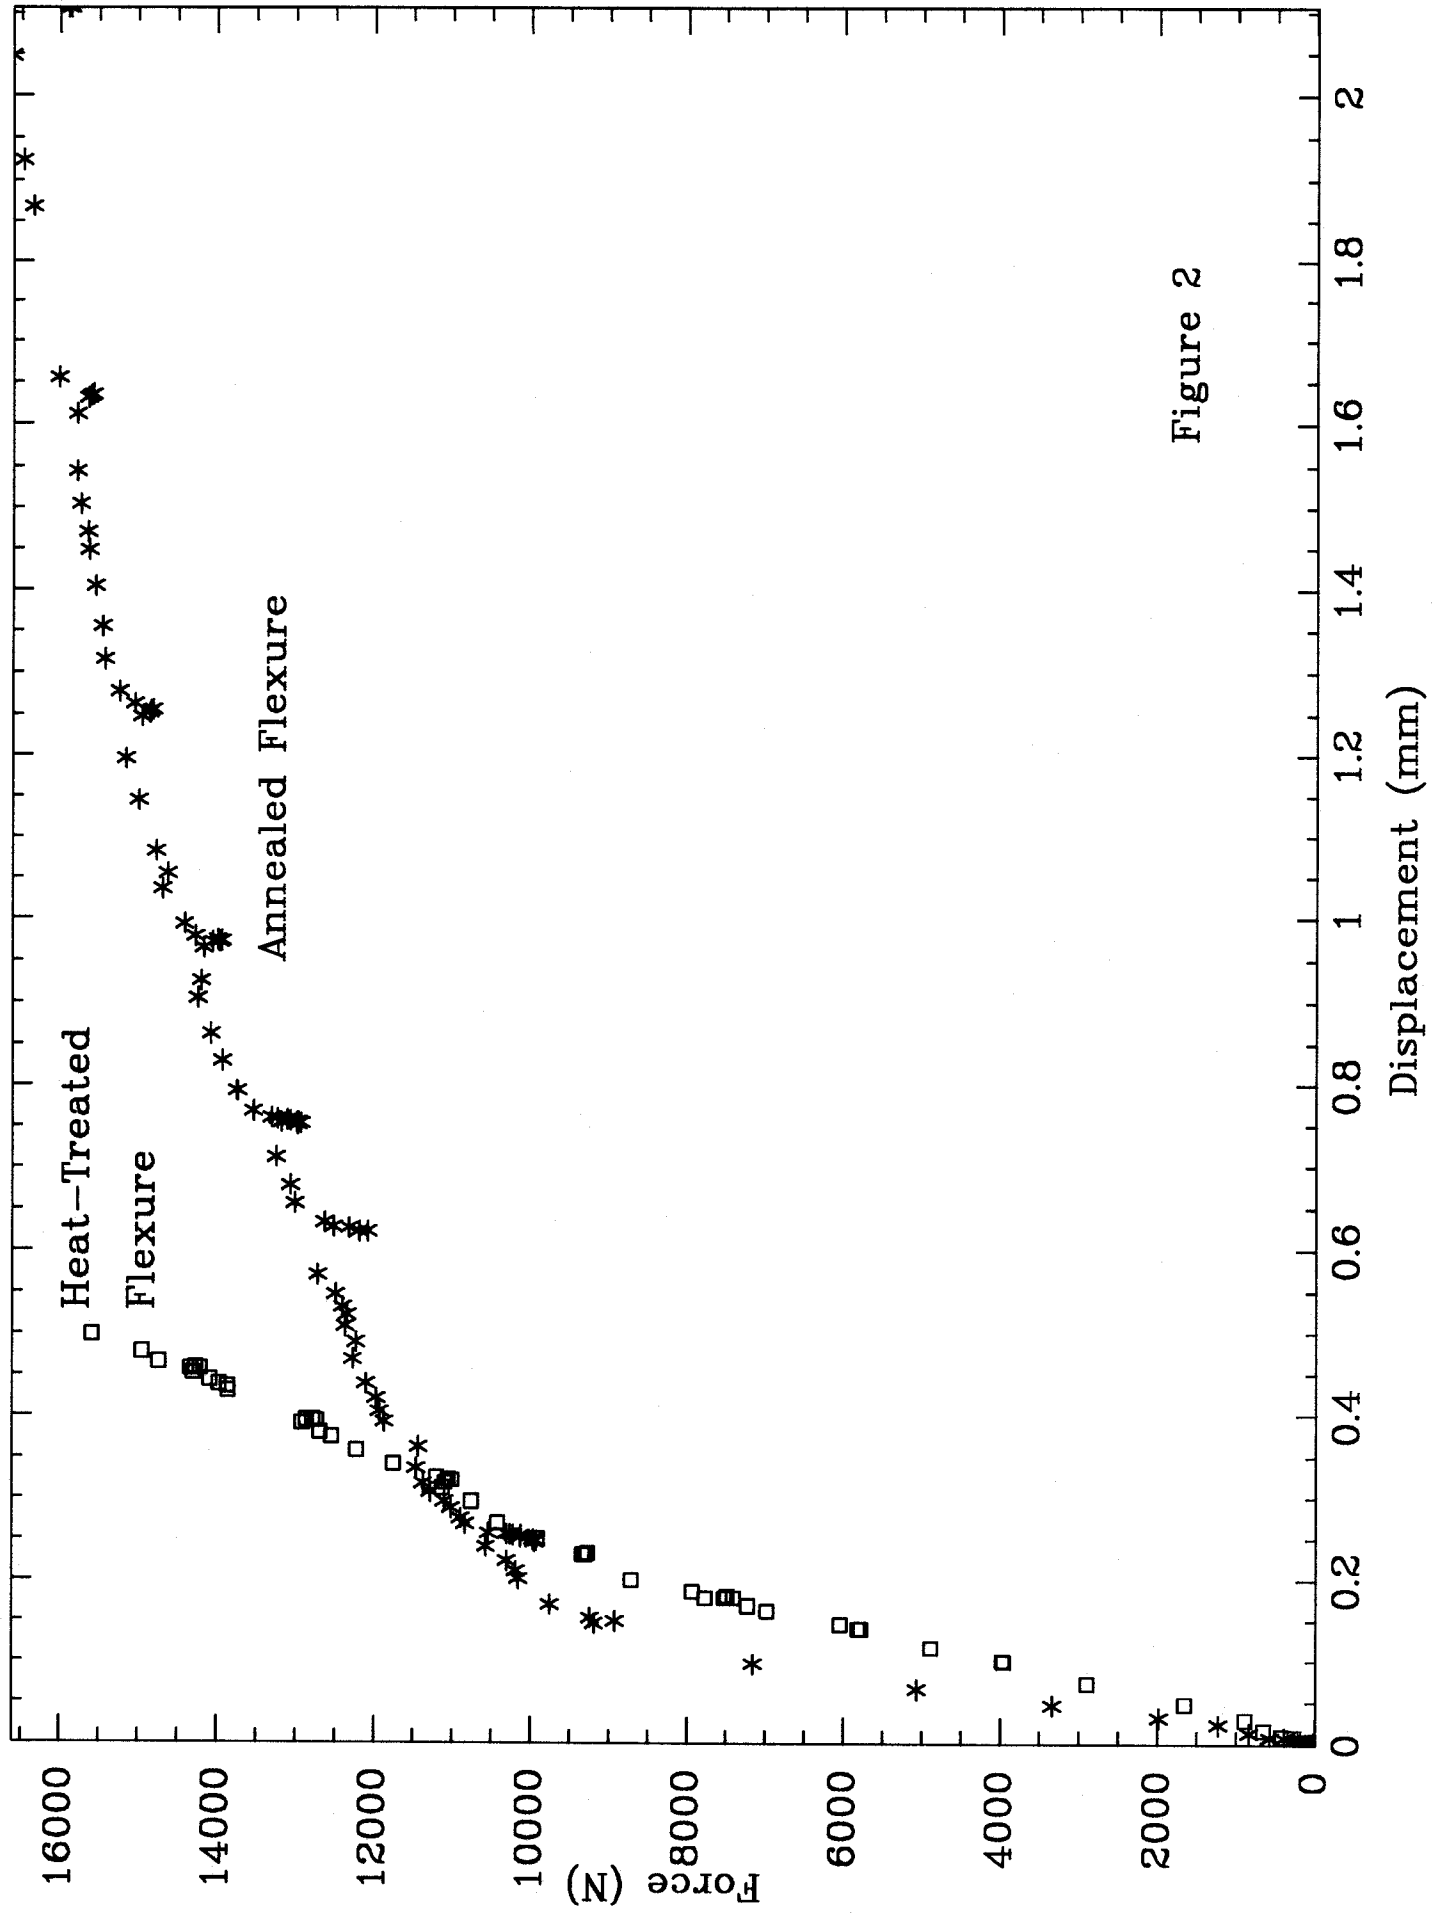


Figure 2

Shear vs. Strain


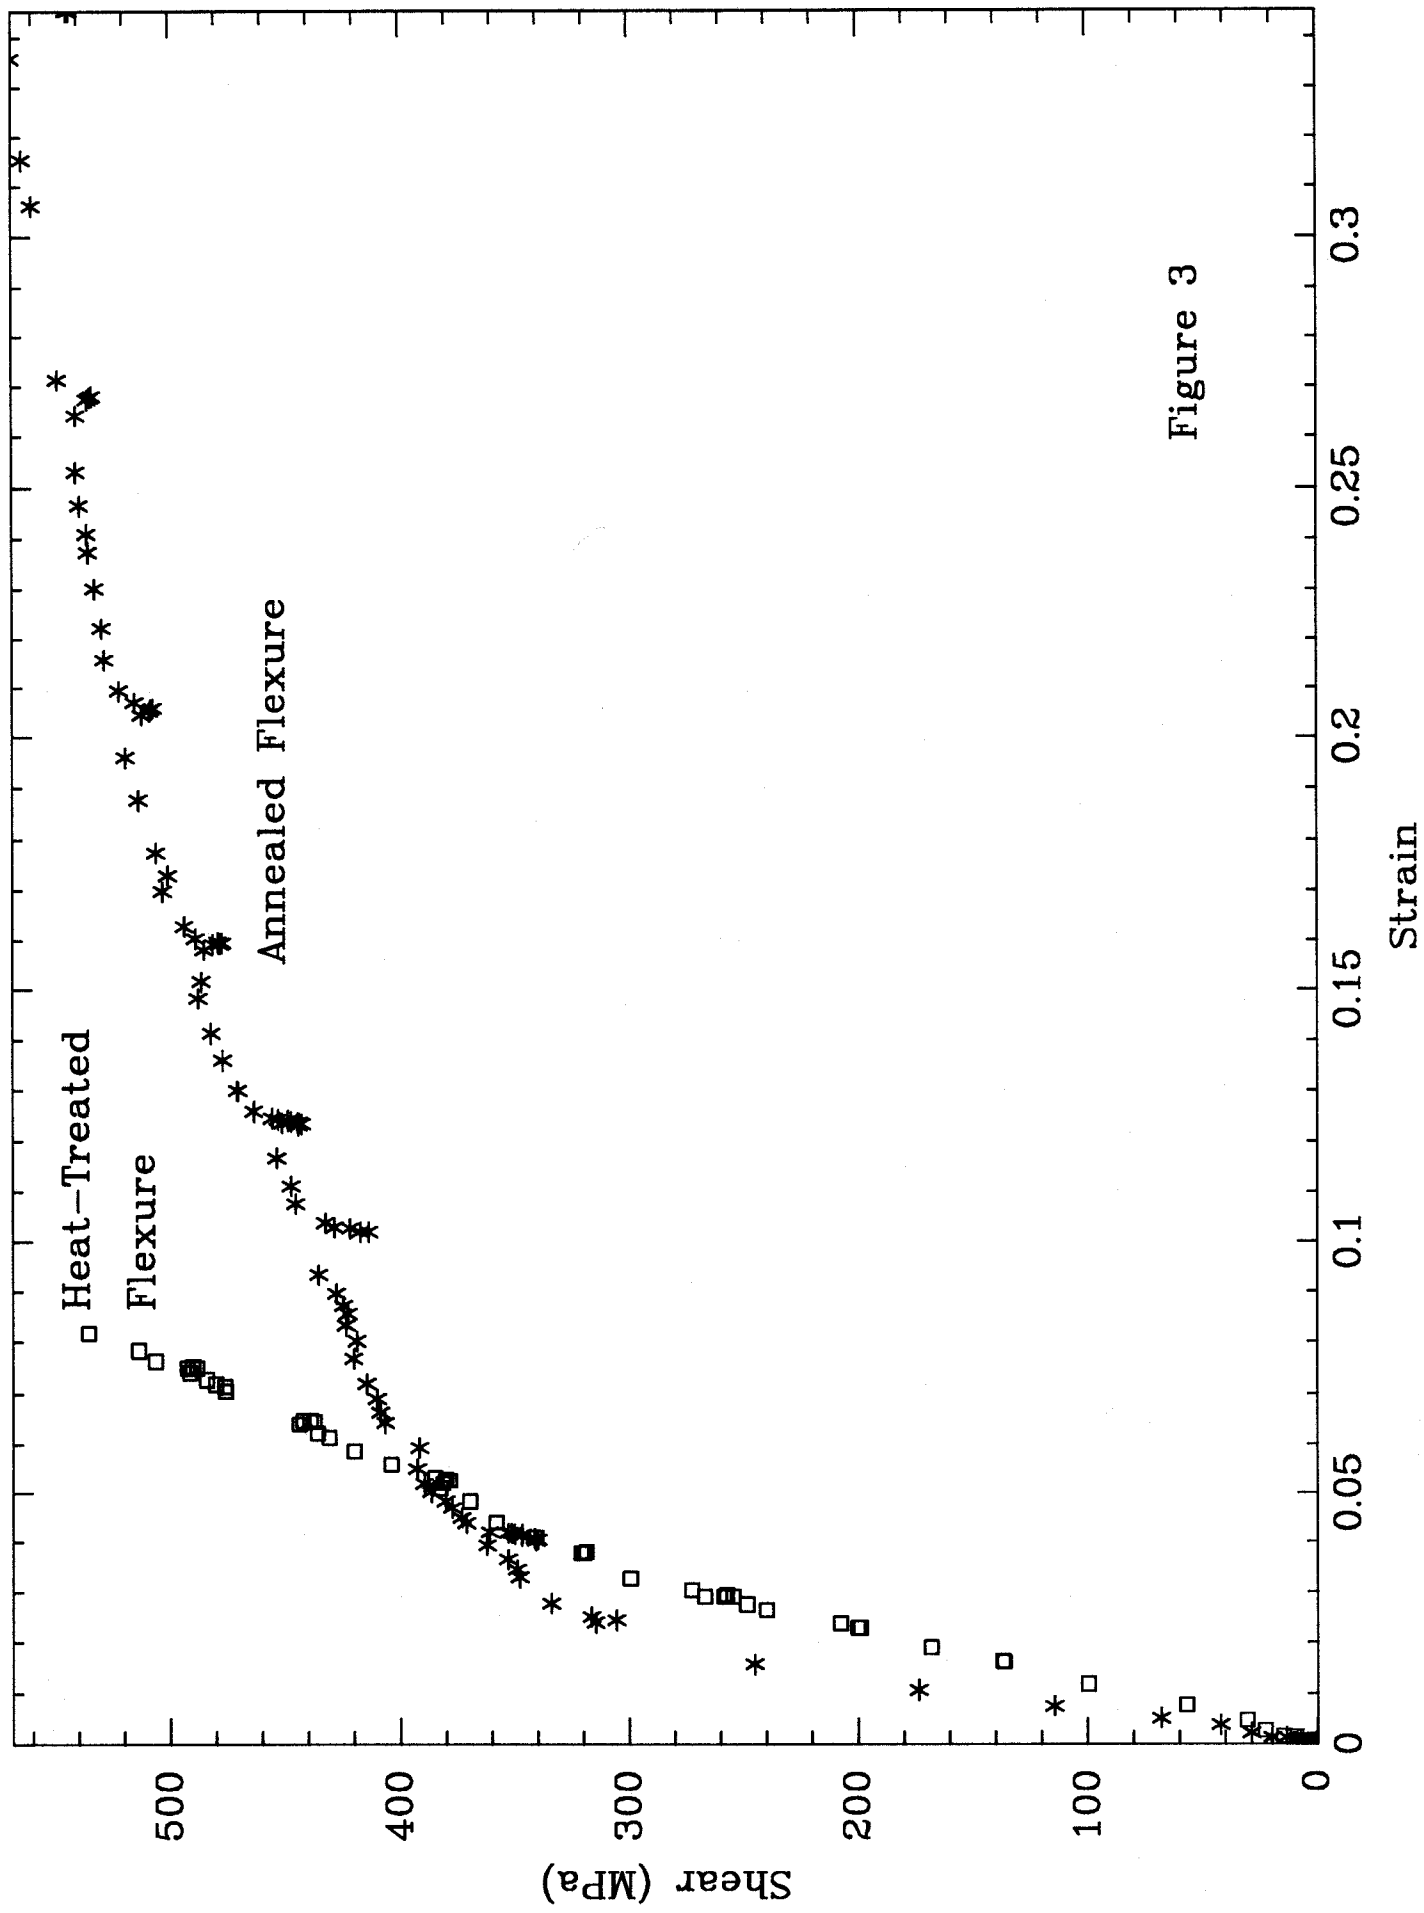


Figure 3

REVISIONS		
REV	DESCRIPTION	DATE

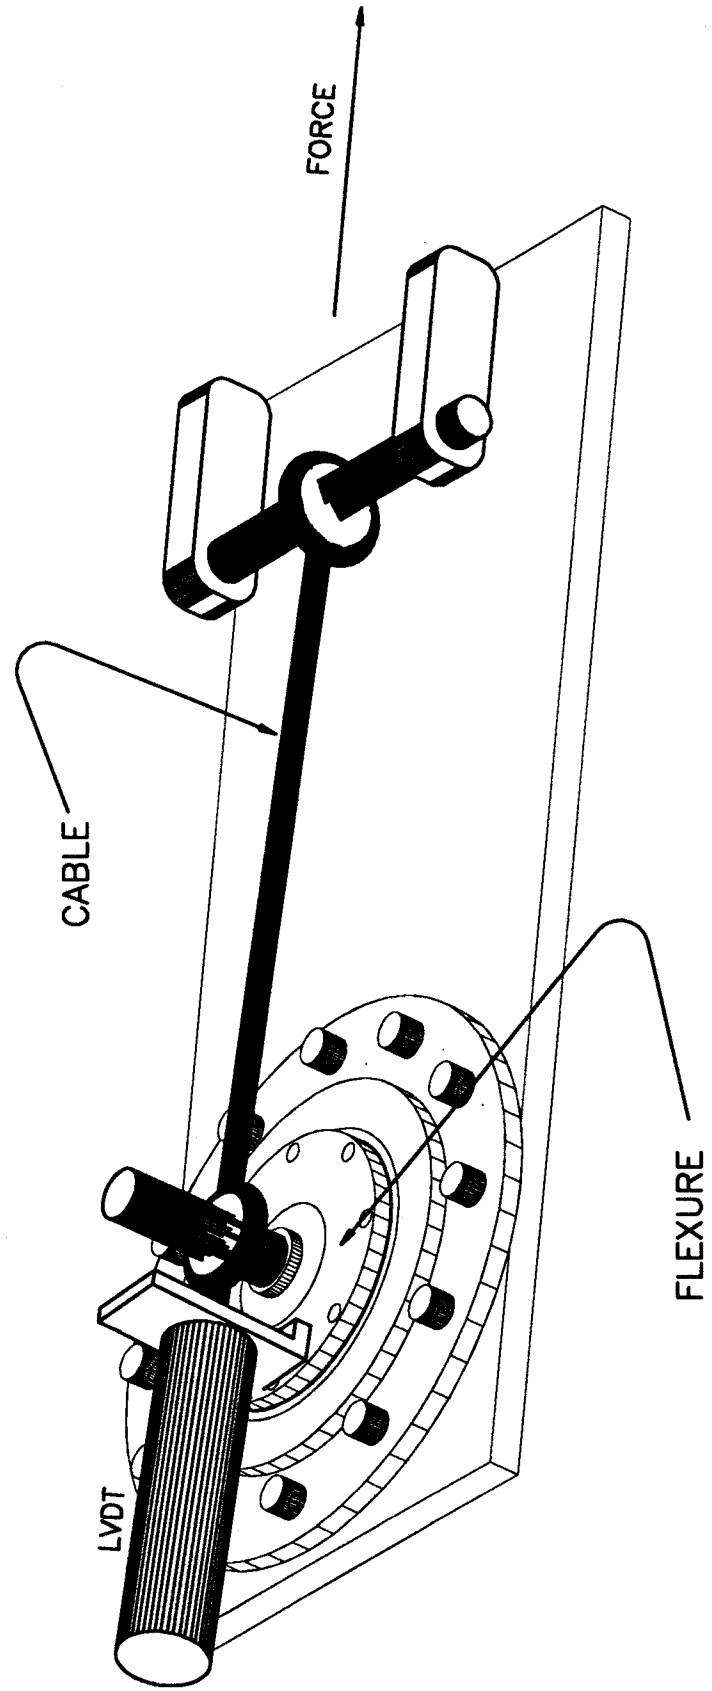

UNLESS OTHERWISE SPEC.		DRAWN BY	DATE	UNIVERSITY OF ARIZONA & SMITHSONIAN INSTITUTION MULTIPLE MIRROR TELESCOPE OBSERVATORY TUCSON, Arizona 85721
TOLERANCES UNLESS OTHERWISE SPECIFIED:		M.D. MCGEUN	02/21/94	
DECIMALS	FRACTIONS	CHECKED BY		TITLE:
.XXX	XX	SHOP CHECK BY		FLEXURE TEST FIXTURE 2
±.010	± 1/16	APPROVED BY		SCALE:
	± 0.30°	APPROVED BY		1" = 2"
DIMENSIONS ARE IN ENGLISH & METRIC		APPROVED BY		REV.
MATERIAL				MMT0024
1" STEEL ROUND STOCK				CAD FILE: MMT0024
FINISH				SHEET NO. 1

FIGURE 4

# Moment vs. Rotation

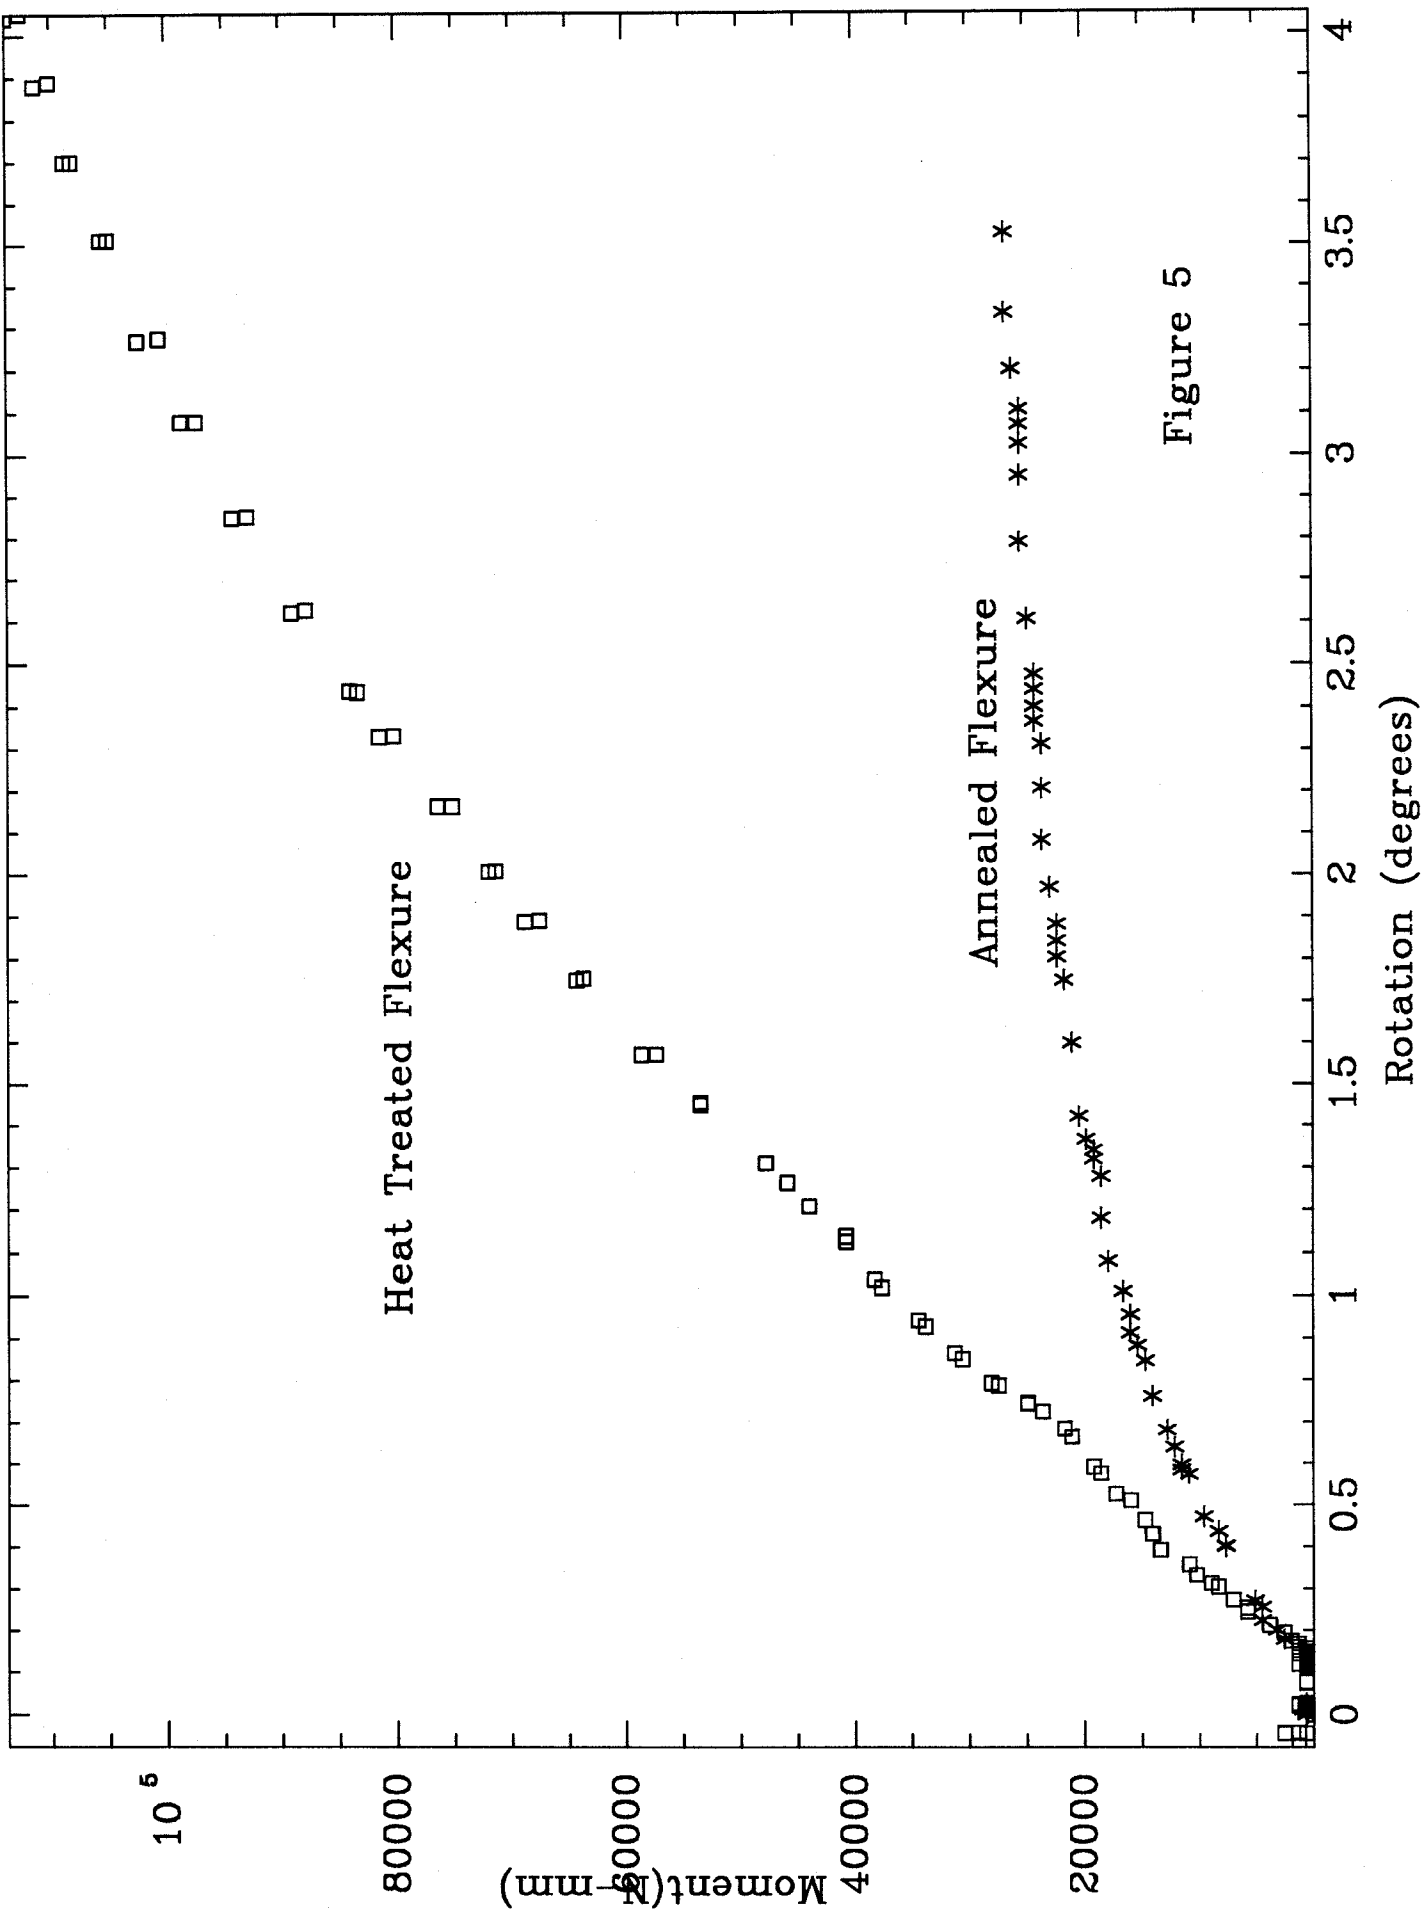


Figure 5

# Normal Stress vs. Rotation

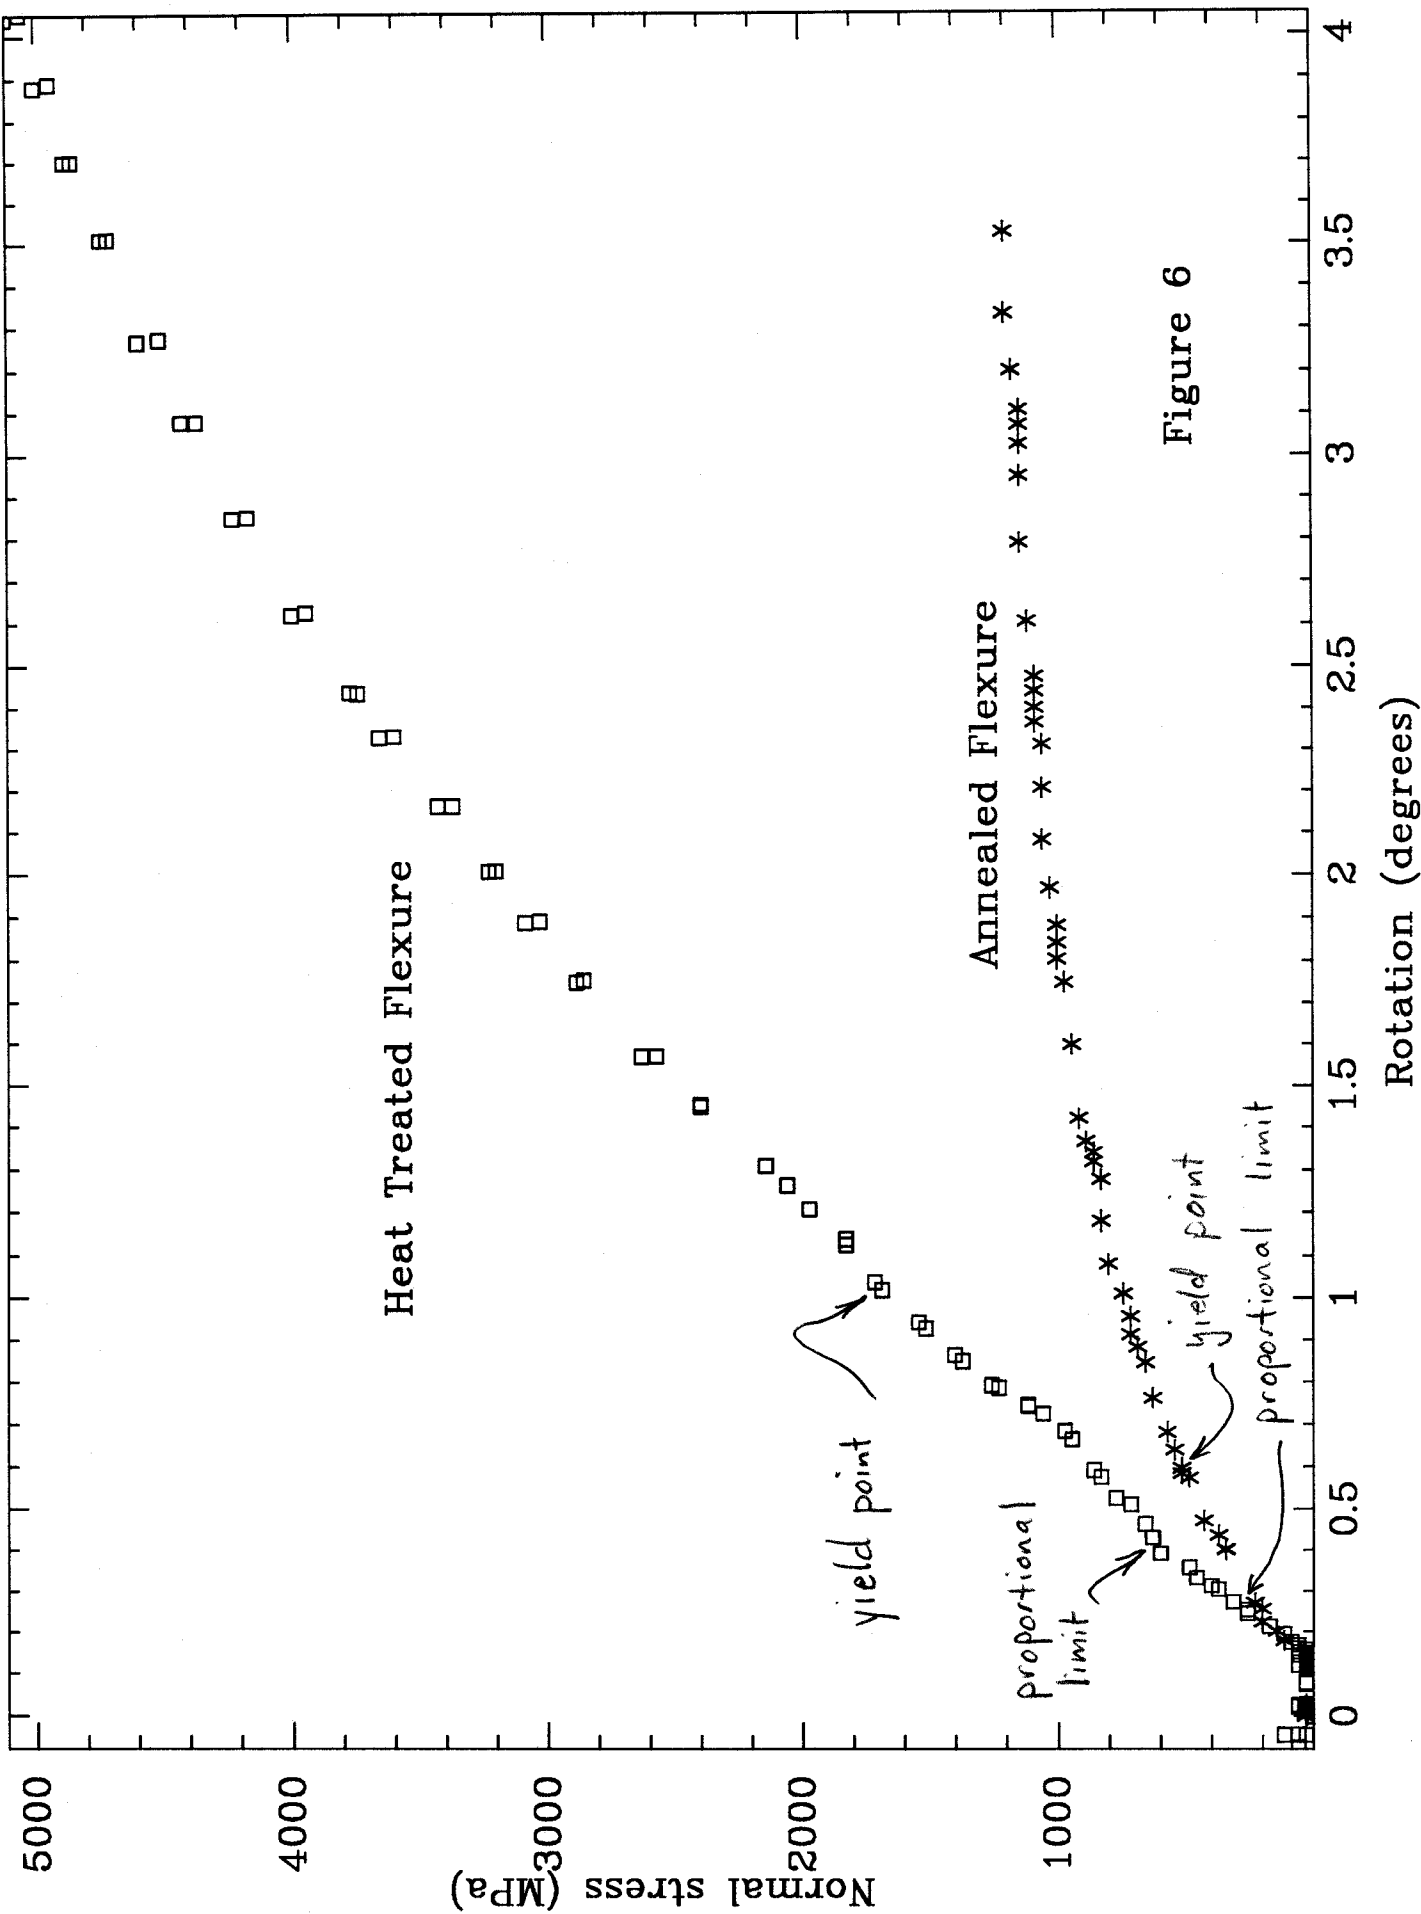


Figure 6